

EXTRACTION AND CHARACTERISATION OF CASSAVA PEEL WAX

C. V. Abiaziem^{1*} and I. A. Ojelade¹

¹Department of Science Laboratory Technology, Federal Polytechnic Ilaro P.M.B 50, Ilaro, Ogun State, Nigeria.

*Corresponding author E-mail: vyvycox@yahoo.com

Abstract

Cassava peel has become conspicuous environmental waste which affects the natural integrity of the environment. Several works have extracted wax from agro-wastes such as sugarcane bagasse, banana peel, apple pomace etc. In this study wax was extracted from cassava peel using soxhlet extraction method with a mixture of benzene and methanol as the extracting solvents. The percentage yield of crude wax was 8.51 % on wet basis. The wax extracted was characterised using Fourier transformed infrared spectroscopy (FT-IR) and ultraviolet-visible spectroscopy (UV-Vis). The physicochemical properties were also studied: acid value, saponification value, ester value, melting point and iodine value. The FT-IR prominent peaks were obtained at 3224(-OH), 2928 (-CH₂), 1376.96 (-CH₃), 1708 (-CHO), 1035 and 885, indicating the presence of alcohols, alkanes, aldehydes, and lignin compounds, respectively. The UV-Vis analysis showed fatty acids, conjugated dienes and hydroperoxides at 232 nm and conjugated trienes at about 255 nm. The results of the physicochemical properties were evaluated: acid value, saponification value, ester value, melting point and iodine value as 23.4 mg/KOH/g, 103.42 mg/KOH/g, 80.02 mg/KOH/g 63.5 °C and 90.3 g/100g values, respectively. This study revealed that wax obtained from cassava peel is a potent product for diverse industrial applications.

Keywords: cassava peel, wax, extraction, characterisation, FT-IR, UV-Vis.

1.0 Introduction

Cassava peels are agro-waste resources discarded after peeling the tuber. It can represent 5 to 15 % of the root^{1,2}. They are obtained after the tubers have been water-cleansed and peeled mechanically¹. They may contain high amounts of cyanogenic glycosides and have higher protein content than other tuber parts³. Cassava peel wax gets extracted using soxhlet extraction method with a mixture of benzene and methanol. The wax portion finds its applications in cosmetics, paper coating, textiles, fruit and vegetable coating, leather sizing, lubricants, adhesives, polishes, and pharmaceutical industry. Hence, it can be considered as an alternative to costly carnauba wax, candelilla wax and chitosan for edible coating applications. Ash gourd peel was found as a good source of wax which was used as edible coat for strawberries to enhance their shelf life⁴. The

present study was aimed at adding value to cassava by using their peels as raw material to extract wax. This also proffers solution to the problem of indiscriminate disposal of peels of cassava, which creates nuisance in the environment. The utilization of cassava peel (agricultural wastes) into wax is considered a potent product for various industrial applications.

2.0 Materials and Methods

2.1 Sample Collection. Cassava peels (agro-waste) were collected from a local cassava processing settlement. The sample was stored in sacks adequately. The sample was washed to remove dirt and dried to a constant weight in a hot air oven at 80°C after which it was triturated in a mill into fine powder and stored in plastic containers.

2.2. Wax Extraction. Wax was extracted from cassava peels as reported by⁵. The cassava peel powder was extracted using soxhlet extraction method with benzene and ethanol mixture of 2:1 v/v for 8 hours to remove wax. The solvent was later evaporated using rotary evaporator (Buchi, Switzerland), and the residue primarily contained wax mixtures with some impurities. The residue was dissolved in isopropanol and was refluxed with charcoal for 1-2 hours to remove any undesirable colour or pigments present. The extract was then filtered to remove the charcoal and evaporated at 60°C to obtain crude wax.

2.3 Physicochemical Analysis.

2.3.1 Acid Value. 5.0 g of wax was weighed into a dry conical flask, 25 ml of absolute ethanol and 2 drops of phenolphthalein indicator were added to the mixture. The mixture was heated with continuous shaking in water bath for 10 min and cooled. The cooled mixture was titrated against 0.1 N KOH solution until pink colour appeared. The acid value was calculated

2.3.2 Saponification Value. 2 g of the wax sample was weighed into a 250 ml conical flask and 25 ml of alcoholic potassium iodide was dissolved in it. A reflux condenser was attached and the flask content was heated on a boiling hot water for 1 hour with occasional shaking, 3 drops of phenolphthalein indicator was added and then titrated with 0.5 N HCl. This was repeated for blank sample.

2.3.3 Iodine Value Determination. 2g of the wax was weighed, 10 ml of chloroform and 30ml of Hannus solution was added into a 250 ml conical flask, the flask was sealed with parafilm and the solution was agitated for 30 min. A mixture of 10 ml of 15 % potassium iodide and 10 ml of distilled water was added. The iodine solution was titrated against 0.1 N sodium thiosulphate solution using starch as an indicator. This was repeated for blank.

2.3.4 Melting Point. The melting point of cassava peel wax was done according to the method adopted by⁶. The wax was melted by warming it in a hot water bath and the melting point was

determined by the capillary tube method or the drop point method. Melted wax was introduced in a 10 cm long and 2mm internal diameter thin-wall hollow capillary tube, until reaching a height of about 1 cm. After that, the capillary tube, containing the wax, was introduced into a bath of water that was slowly warmed at 1–2 °C/min; the temperature was studied with a thermometer (with an accuracy of 0.1 °C) whose bulb had to be as close as possible to the beeswax column introduced in the capillary tube.

2.4 Characterisation

2.4.1 *Fourier Transform Infrared Analysis.* For the analysis, wax sample was placed on the diamond crystal and the ATR holder was screwed onto the sample to have a good contact with the crystal. The PerkinElmer spectrum 400 FT-IR spectrometer was set to scan 60 times at a resolution of 2.0cm^{-1} over the wavelength range of 4000cm^{-1} to 650cm^{-1} against the transmittance. After every scan, the baseline was corrected using the background spectrum previously obtained from the blank.

2.4.2 *UV-Vis Analysis.* A known quantity of wax (0.1% w/v) was dissolved in hexane for spectroscopic measurement. The solvent was scanned across wavelength of 200 to 600 nm by using Helios α spectrophotometer (Thermo Electron Corporation, USA).

3.0 Results and Discussion

3.1. *Yield of Cassava Peel Wax.* The yield of wax from cassava peel was 8.51%. This yield was high compared to that reported by⁷ which was found to be 0.95% (w/w). This could be as a result of the selective extractability of the main components in wax, a mixture with different polarities (mass ratio of benzene and methanol, 2:1), as this mixture could efficiently extract both polar and nonpolar compounds and give a high wax yield from cassava peel.

3.2 *Physicochemical Analysis.* Table 3.1 shows the results of the physicochemical parameters of the wax extracted. In this present study, wax from cassava peel which is crude in nature showed a melting point of 65.5 °C, which was comparable to that reported by^{7,6} which were 62.12 °C and 62.39 °C, respectively. However, it was found to be higher than that reported by⁸ which was 55-56 °C. The acid value, saponification value and ester value was lower compared to that reported by⁷, which was 129.15(mg/KOH/g), 374.58(mg/KOH/g) and 245.08(mg/KOH/g), respectively but was comparable to that reported by⁸ which was 22.33 ± 0.39 (mg/KOH/g), 98.04 ± 0.86 (mg/KOH/g) and 75.58 ± 0.84 (mg/KOH/g), respectively.

3.3 *FT-IR Analysis.* Figure 3.1 presents the FT-IR spectra of wax from cassava peel (CP). FT-IR analysis of wax sample revealed the presence of several organic functional groups present in crude wax indicating their respective compounds. A broad and blunt IR absorption band was observed

in the region of 3424 cm^{-1} , this reveals that the wax possesses hydroxyl group O–H stretching. The strong absorption bands at 2928 cm^{-1} indicates the presence of –CH stretch and bend while 1381 cm^{-1} reveals the presence of CH_3 group, which are characteristics of aliphatic fraction of the wax. Similarly, bands at 1708 cm^{-1} and 1035 cm^{-1} showed the presence of –C=O stretch but represented two different functional groups; aldehydic and carboxylic acid and it is also assigned to carbonyl stretching in fatty acids. The FT-IR spectra of cassava peel wax exhibited similar absorption patterns with those reported by ^{8, 9, 6}.

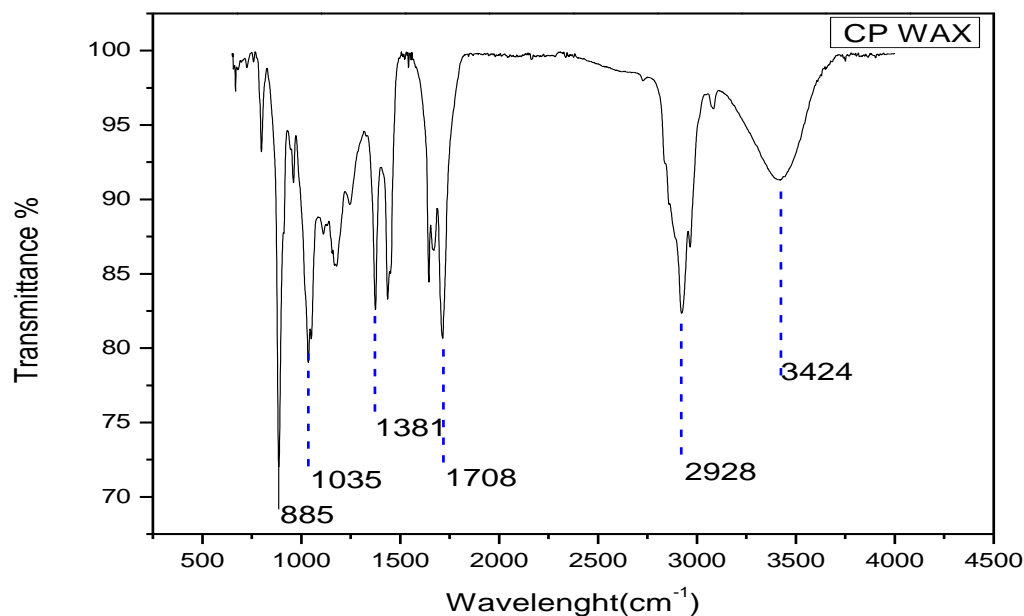


Figure 3.1: FT-IR Spectra of Crude Wax from Cassava Peel

3.4 UV-Vis Analysis. Fatty acids, conjugated dienes, and hydroperoxides formed as a result of lipid oxidation absorbed UV light at about 232 nm and conjugated trienes at about 255 nm. In the UV range of 100–400 nm, cassava peel wax showed sharp peaks near 255 nm indicating the presence of conjugated dienes and trienes as presented in Figure 3.2. Also, in 400–600 nm range no peak was found indicating the absence of carotenoids. This result was similar to that reported by⁷, which showed sharp peaks near 230 and 270 nm indicating the presence of conjugated dienes and trienes. The result of the cassava peel was in agreement with that reported by⁸.

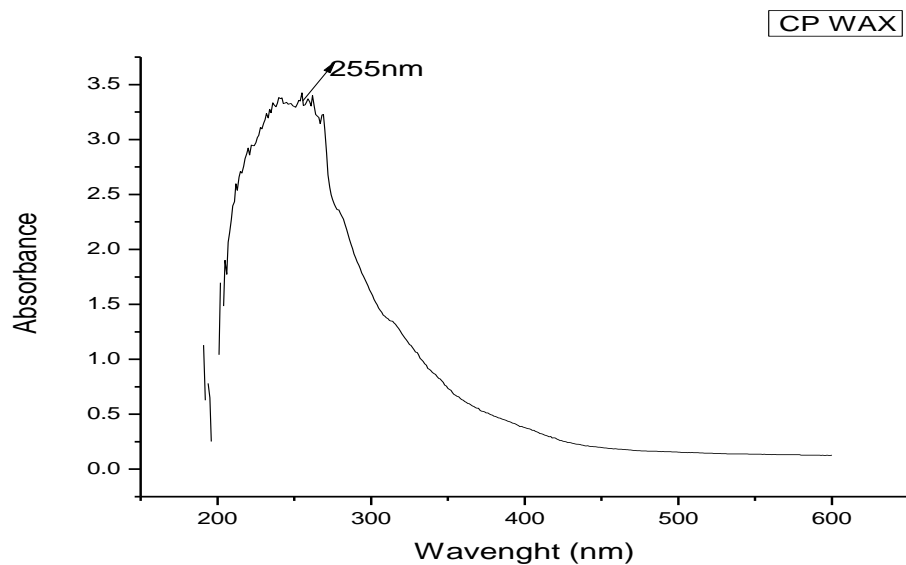


Figure 3.2: UV-Vis Spectra of Crude Wax from Cassava Peel.

Table 3.1: Physicochemical Properties of Extracted Cassava Wax

Physicochemical Parameters	Cassava Peel Wax
Odour	Agreeable odour
Nature	Viscous
Melting point (°C)	63.5
Acid value (mg/KOH/g)	23.4
Saponification value (mg/KOH/g)	103.42
Iodine value (g/100g)	90.03
Ester value (mg/KOH/g)	80.02

Table 3.2: FT-IR Spectra of Crude Wax from Cassava Peel

Band Position	Assignment
3,443	O–H stretching vibration (associated to water or alcohols)
2,928	Asymmetric CH ₂ stretching (associated to aliphatic fraction)
1,708	Carbonyl stretching in fatty acids
1,381	CH ₂ bending vibrations (associated to lignin or wax)
1,035	C–H deformation in guaiacyl unit (associated to lignin)
885	Aromatic C–H out-of-plane vibrations (associated to lignin)

4.0 Conclusion

The yield of crude wax from sugarcane peel was 8.51% (w/w). This study showed the presence of various classes of compounds like alkane, ester, alcohol, fatty acids, etc. present in cassava peel wax. Alkane heneicosane finds its utilisations as insect semiochemical. The present of fatty acids played a significant role in human nutrition which was found in the wax. The wax extracted has reasonable physicochemical characteristics comparable to those studied in literatures. Thus, cassava peel wax has many compounds of biological and industrial importance.

Acknowledgment

The authors sincerely appreciate the financial contributions of TETFUND (Nigeria), through The Federal Polytechnic Ilaro and NRF/RISA (South Africa) and the support of Environmental and Nano Science Group, Chemistry Department, University of the Western Cape, Cape Town, South Africa for providing laboratory space for our research.

References

- [1] S. O., Aro, V. A., Aletor, O. O. Tewe & J. O. Agbede. (2010). Nutritional potentials of cassava tuber wastes: A case study of a cassava starch processing factory in south-western Nigeria. *Livestock Research for Rural Development* 22 (11), 105-106
- [2] S. O. Nwokoro & E. I. Ekhosuehi, (2005). Effect of replacement of maize with cassava peel in cockerel diets on performance and carcass characteristics. *Tropical Animal Health Production* 37 (6), 495-501.
- [3] O. O. Tewe, (2004). The global cassava development strategy: cassava for livestock feed in Sub-Saharan Africa. IFAD and FAO.1-75.

- [4] K. M. Srinivasan, K. Chaudhari, and S. S. Lele. (2011). "Ash gourd peel wax: extraction, characterisation, and application as an edible coat for fruits," *Food Science and Biotechnology* 20(2), 383–387.
- [5] K., Anuj, S. N., Yuvraj, C. Veena, & Nishi, K. B. (2013). Characterisation of cellulose nanocrystals produced by acid-hydrolysis from sugarcane bagasse as agro-waste. *Journal of Materials Physics and Chemistry* 2(1), 1-8.
- [6] T., Bekele, B. Desalegn & E. Mitiku (2015). Analysis of physico-chemical properties of beeswax produced in Bale natural forest, South-Eastern Ethiopia, *European Journal of Biophysics. Special Issue: Environmental Toxicology* 4(5), 42-46.
- [7] B. Mangesh & S. S. Lele. (2012). Extraction and characterisation of sugarcane peel wax. *International Scholarly Research Network ISRN Agronomy* (2012), 1-6. Article ID 340158. doi:10.5402/2012/340158.
- [8] Y., Athukorala, G., Mazza & B. D. Oomah. (2009). Extraction, purification and characterisation of wax from flax (*Linum usitatissimum*) straw. *European J, of Lipid Sci, and Tech.* 111(7), 705–714.
- [9] U. Knuutinen & A. Norrman, (2000). Wax analysis in conservation objects by solubility studies, FTIR and DSC. *Proceedings of the 15th World Conference on Nondestructive Testing, Rome, Italy.*